زجاج زجاجة الناشر القصب مربع المورد

[redacted]

قوتنا

الصين زجاجة مربع ريد الناشر الزجاج المزود

10000 متر مربع ديكور ملكية الورشة.

20 نوعا من آلات الديكور المختلفة.

20 عاما من الخبرة فى مجال الديكور.

20 مستقرة تعاون مصنع الزجاج ، مصنع السيراميك ، مصنع علب الهدايا ، مصنع الغطاء المعدني ، دعم مصنع الغطاء الخشبي.

العلامات التجارية العالمية الشهيرة التي تصنع مثل بورش وأرماني وزارا إلخ.

هذه زجاجة الناشر مربع يحمل عطر 5.5 أونصة ، مناسب للمنزل ، الفندق ، المطعم. الشكل المربع يجعل المنتج كلاسيكيًا وأنيقًا.

ميزة المنتج

تأثير العملية

يمكننا إنشاء الشكل .OEM / ODM يقبل تصميم مخصص Cupwind الخاص بك مع / بدون اسم العلامة التجارية. الزخرفة المتاحة للرش ، والطلاء الكهربائي ، والطلاء المعدني ، والشارات ، والختم الساخن ، والشاشة الحريرية ، والرمل ، ونقل المياه ، إلخ.

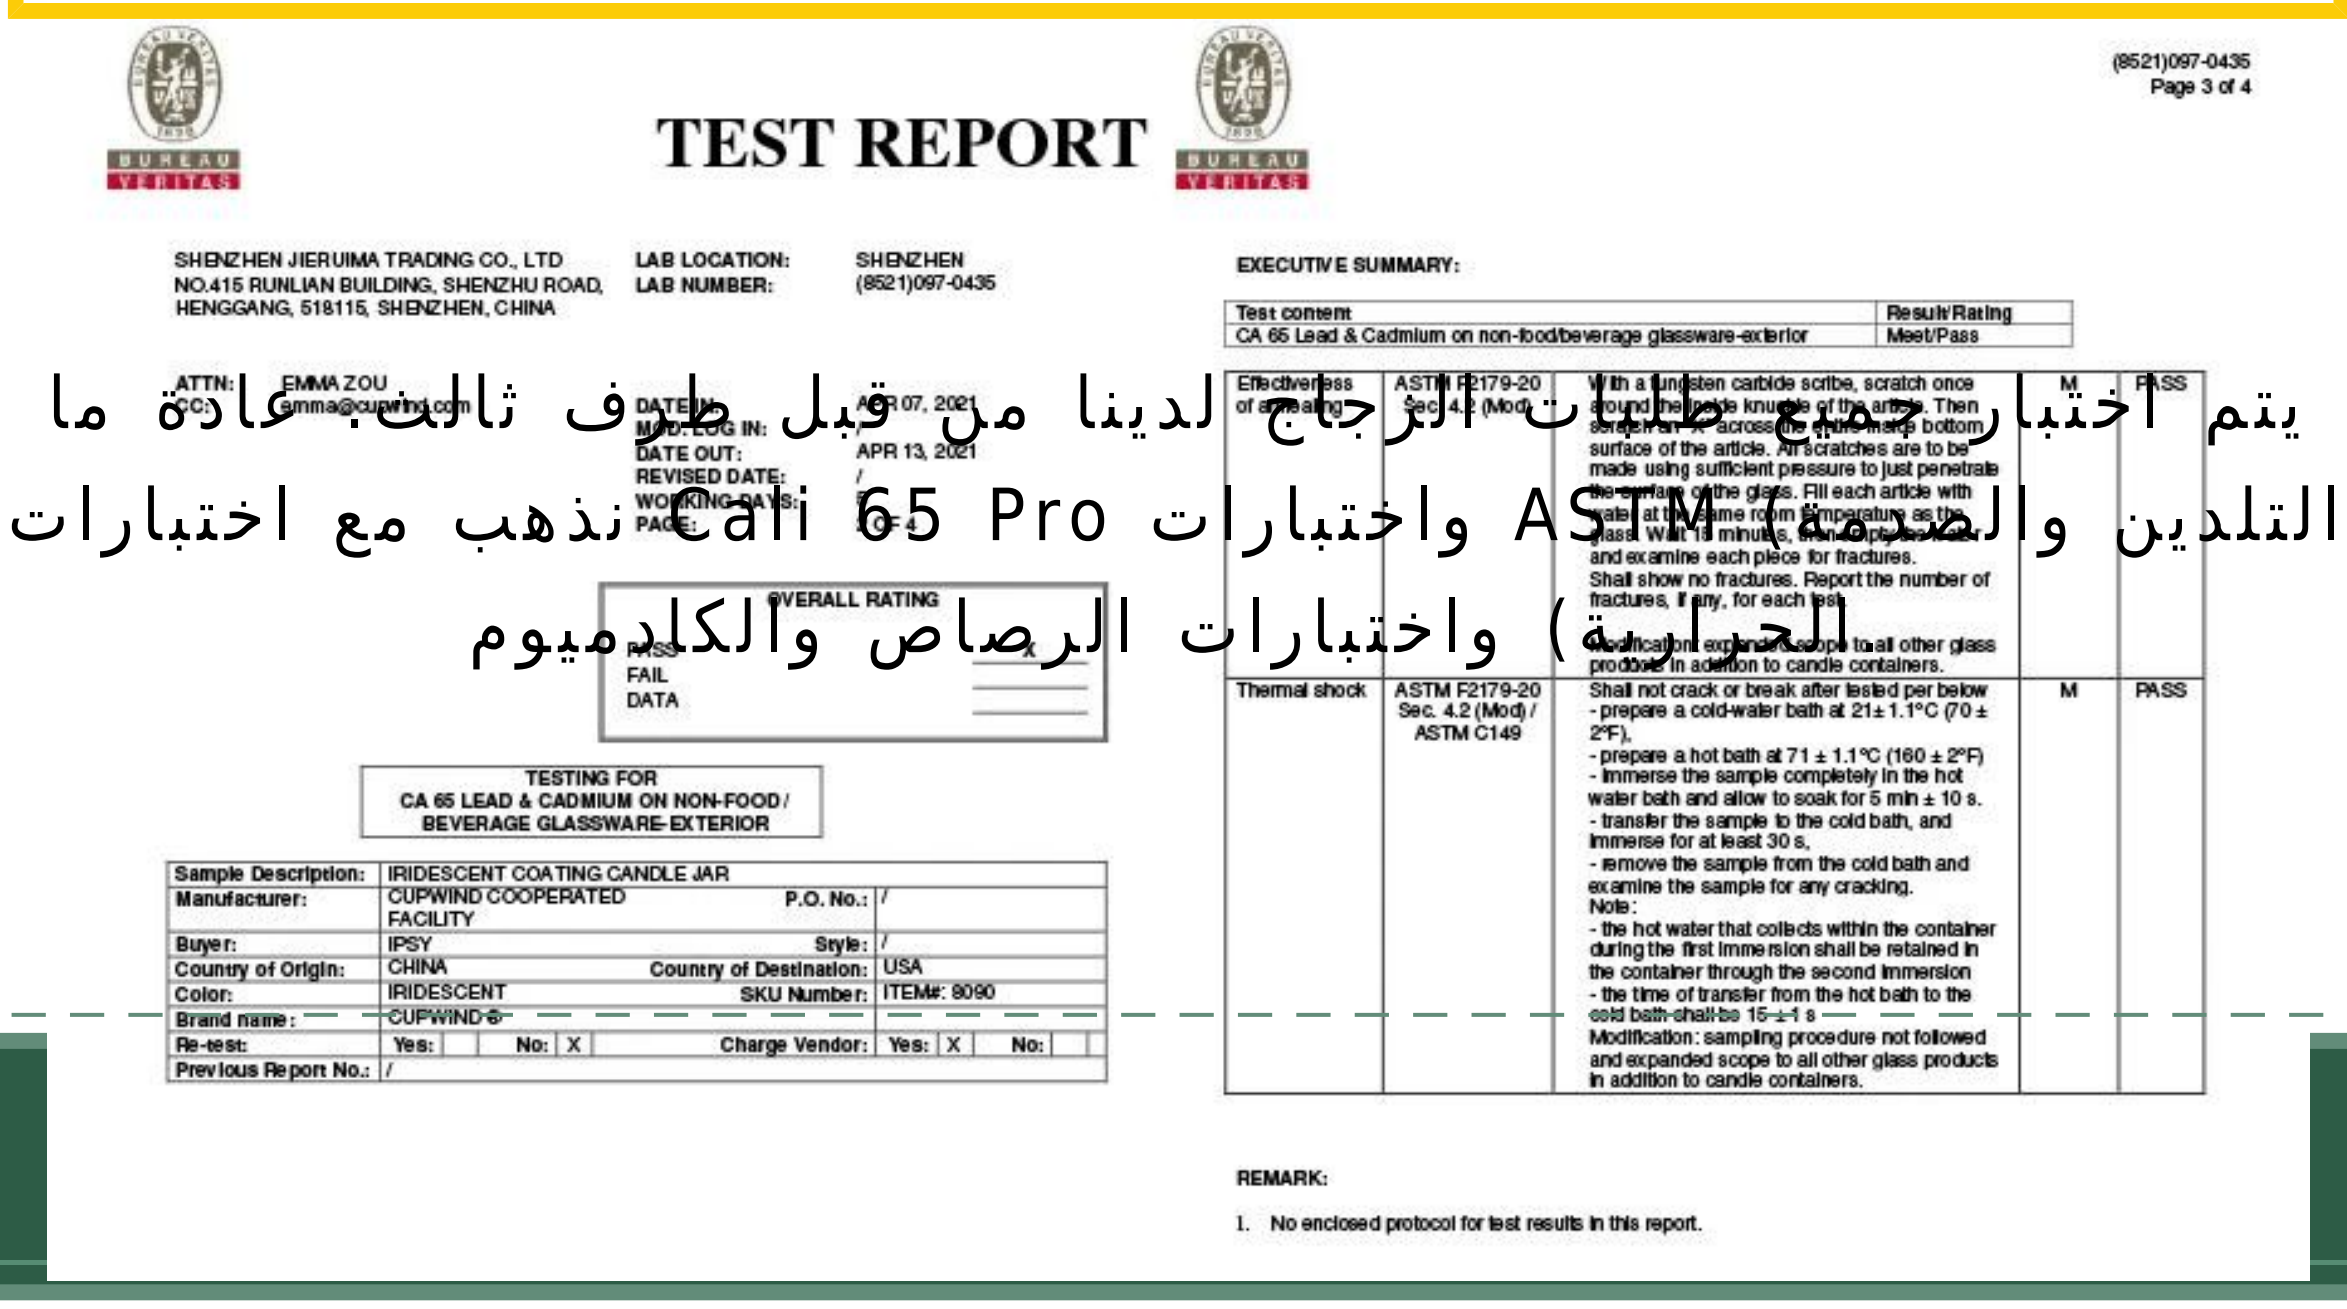

TEST REPORT

(8521)097-0435
Page 3 of 4

SHENZHEN JIERUIMA TRADING CO., LTD
NO.415 RUNLIAN BUILDING, SHENZHU ROAD, HENGGANG, 518115, SHENZHEN, CHINA

LAB LOCATION: SHENZHEN
LAB NUMBER: (8521)097-0435

ATTN: EMMA ZOU
CC: emma@cupwind.com

DATE IN: APR 07, 2021
MOD. LOG IN: /
DATE OUT: APR 13, 2021
REVISED DATE: /
WORKING DAYS: [illegible]
PAGE: 3 OF 4

OVERALL RATING
PASS X
FAIL
DATA

TESTING FOR
CA 65 LEAD & CADMIUM ON NON-FOOD / BEVERAGE GLASSWARE-EXTERIOR

Sample Description:	IRIDESCENT COATING CANDLE JAR		
Manufacturer:	CUPWIND COOPERATED FACILITY	P.O. No.:	/
Buyer:	IPSY	Style:	/
Country of Origin:	CHINA	Country of Destination:	USA
Color:	IRIDESCENT	SKU Number:	ITEM#: 8090
Brand name:	CUPWIND®		
Re-test:	Yes: No: X	Charge Vendor:	Yes: X No:
Previous Report No.:	/		

EXECUTIVE SUMMARY:

Test content	Result/Rating
CA 65 Lead & Cadmium on non-food/beverage glassware-exterior	Meet/Pass

Effectiveness of annealing	ASTM F2179-20 Sec. 4.2 (Mod)	With a tungsten carbide scribe, scratch once around the inside knuckle of the article. Then scratch an X across the [illegible] bottom surface of the article. All scratches are to be made using sufficient pressure to just penetrate the surface of the glass. Fill each article with water at the same room temperature as the glass. Wait 15 minutes, then [illegible] and examine each piece for fractures. Shall show no fractures. Report the number of fractures, if any, for each test. Modification: expanded scope to all other glass products in addition to candle containers.	M	PASS
Thermal shock	ASTM F2179-20 Sec. 4.2 (Mod) / ASTM C149	Shall not crack or break after tested per below - prepare a cold-water bath at 21±1.1°C (70 ± 2°F), - prepare a hot bath at 71 ± 1.1°C (160 ± 2°F) - immerse the sample completely in the hot water bath and allow to soak for 5 min ± 10 s. - transfer the sample to the cold bath, and immerse for at least 30 s, - remove the sample from the cold bath and examine the sample for any cracking. Note: - the hot water that collects within the container during the first immersion shall be retained in the container through the second immersion - the time of transfer from the hot bath to the cold bath shall be 15 ± 1 s Modification: sampling procedure not followed and expanded scope to all other glass products in addition to candle containers.	M	PASS

REMARK:

1. No enclosed protocol for test results in this report.

يتم اختبار جميع طلبات الزجاج لدينا من قبل طرف ثالث. عادة ما نذهب مع اختبارات Cali 65 Pro واختبارات ASTM (التلدين والصدمة الحرارية) واختبارات الرصاص والكادميوم

عملية التعبئة والتغليف والبليت

نحن نلف كل منهما زجاج زجاجة الناشر بواسطة كيس مقابل للابتعاد عن الغبار ، ثم الكرتون المموج مع فواصل الألواح المتقاطعة. دائمًا ما وسنضيف شبكة قطنية ، LCL تكون المنصات الخشبية فعالة لشحنات في مكان الباب للحماية من السقوط عند فتح باب الحاوية.